

APG-760 Phosphate Laser Glass

For High Power Applications at 1.05 μm

Product information

APG-760 is our next generation of our advanced laser glasses with increased thermo-mechanical properties. We recommend it be used as active material in laser systems with high repetition rates. The glass will be available in doping levels from 1 % to 4 % Nd³⁺. All properties displayed apply to all doping levels, if not otherwise indicated.

Applications

- High Power Applications
- Material processing

Quality assurance

Quality control is conducted under rigorous final inspection of the finished component. Selected glass properties and doping levels are measured for every melt. Measurements include chemical composition control, a range of photometric measurements, physical property testing and inspection of internal quality.

Forms of supply

The glass is available as fully finished components, such as rods, slabs and discs, manufactured according to customer specifications including dielectric coatings (AR, HR, etc.) with high laser damage threshold. Please contact us regarding the availability of the various doping levels are available from stock according to your needs.

Application support

Please contact us with your laser components specification. Our experienced expert application team will find the right solution for your application.



Laser Properties (Calculated, Judd-Ofelt)

| | |
|---|------|
| Emission Peak λ [nm] | 1054 |
| Effective Linewidth [nm] | 29.2 |
| Linewidth FWHM [nm] | 24.9 |
| Radiative Lifetime τ_{rad} [μs] | 376 |
| Emission Cross Section σ_{em} [10^{-20} cm^2] | 3.2 |

Optical Properties

| | |
|---|--------|
| n_d | 1.5328 |
| v_d | 68.54 |
| n_2 [$10^{-20} \text{ m}^2/\text{W}$] (calc.) | 3.01 |
| $dn/dT_{\text{rel.}}$ (1060 nm, 20°–40°C) [$10^{-6}/\text{K}$] | 1.9 |
| $n_{1054 \text{ nm}}$ (calc. from Sellmeier) | 1.5232 |
| $n_{633 \text{ nm}}$ (calc. from Sellmeier) | 1.5312 |
| Stress Optical Coefficient K [$10^{-6} \text{ mm}^2/\text{N}$] (588 nm) | 2.33 |

Sellmeier Coefficients

| | | | |
|----|------------|----|------------|
| B1 | 0.85792298 | C1 | 0.00455294 |
| B2 | 0.46272994 | C2 | 0.01471901 |
| B3 | 0.96370235 | C3 | 104.406880 |

Attenuation Coefficient [cm⁻¹]

| | | | |
|---------|----------|---------|--------|
| 400 nm | ≤ 0.20 | 3333 nm | ≤ 2.00 |
| 1054 nm | ≤ 0.0015 | | |


Physical Properties

| | |
|---|------|
| Density ρ [g/cm ³] | 2.70 |
| Thermal Conductivity $\lambda_{25^\circ\text{C}}$ [W/(m·K)] | 0.76 |
| Thermal Conductivity $\lambda_{90^\circ\text{C}}$ [W/(m·K)] | 0.83 |
| Young's Modulus E [10 ³ N/mm ²] | 74 |
| Poisson's Ratio μ | 0.24 |
| Fracture Toughness, K_{1C} [MPa·m ^{1/2}] | 0.73 |
| Knoop Hardness $HK_{0.1/20}$ | 472 |
| Heat Capacity $c_{p, 20^\circ\text{C}}$ [J/(g·K)] | 0.77 |
| Thermal Expansion $\alpha_{(+20/+300^\circ\text{C})}$ [10 ⁻⁶ /K] | 8.9 |
| Thermal Expansion $\alpha_{(+20/+40^\circ\text{C})}$ [10 ⁻⁶ /K] | 6.1 |
| Transformation Temperature T_g [°C] | 520 |


Chemical Properties

| | |
|---|--------|
| Weight Loss in 50 °C Water [mg/(cm ² d)] | <0.004 |
| SR | 2.3 |
| AR | 3.3 |
| FR | 0 |
| CR | 1 |

Transmission Curve

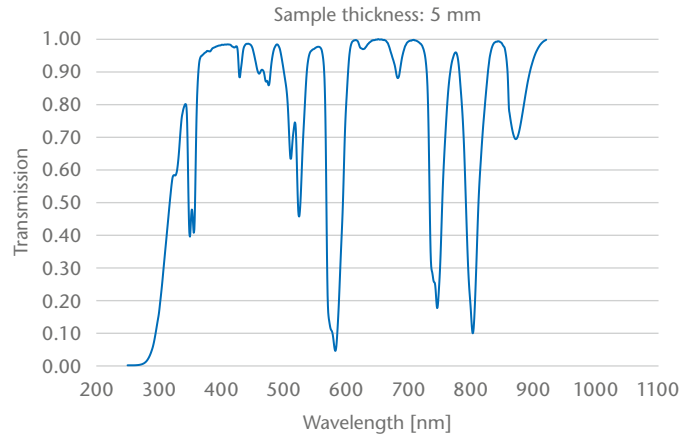

Fluorescence Curve

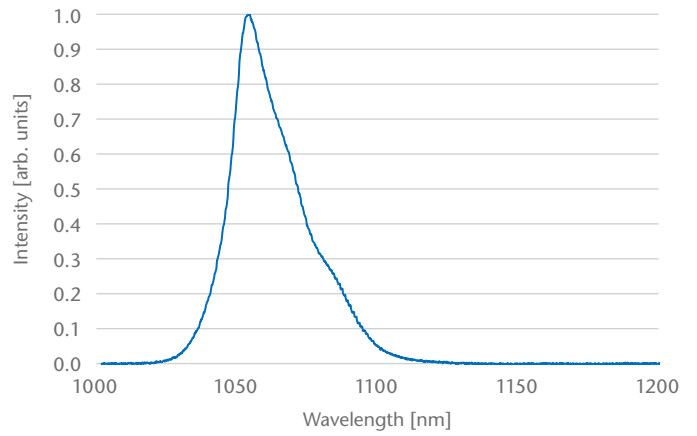

Cross Section

